

ELMET
TECHNOLOGIES

MOLYBDENUM ARC-CAST PRODUCTS

PURE MOLYBDENUM APL Arc-Cast Plate 3203 Low Carbon


This specification covers rolled plate of carbon-deoxidized molybdenum produced from ingots consolidated by the consumable electrode vacuum-arc-casting process.

CHEMICAL CHARACTERISTICS¹

(Mass fraction in % [cg/g]; ppm [μ g/g])

The chemical composition of the sheet used to produce rolled plate shall conform to the following limits:

Mo (By Difference)	min.	99.97 %
O	max.	0.002 %
N	max.	0.002 %
Ni	max.	0.002 %
C	max.	0.010 %
Fe	max.	0.010 %
Si	0.01 -	0.003 %

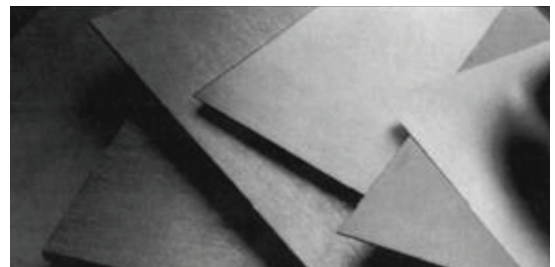

APL

STRUCTURE

Plate will be supplied in the stress-relieved condition unless otherwise requested.

MECHANICAL PROPERTIES

Tensile test will be conducted at room temperature (65°F - 85°F) using a strain rate of 0.002 to 0.005 in/in/min through 0.6 % offset and 0.02 to 0.05 in/in/min to fracture. Tensile properties will be determined on specimens taken transverse to the final rolling direction. Test specimens will be prepared and tested according to ASTM Specification No. E-8, utilizing a gage length of 1 inch.

¹ Information on testing methods on request.

Tensile properties shall meet the following minimum values:

Thickness (inches)	Tensile Strength (psi Minimum)	Yield Strength (.2% Offset) (psi Minimum)	Elongation (% Minimum)
.1875 to .500	95.000	80.000	10
Over .500 to 1.000	85.000	70.000	2*
Over 1.000 to 1.500	75.000	60.000	1*

*Transverse elongation varies according to the amount of reduction and cross-rolling necessary to roll to the desired size in this thickness range. Typical elongation will exceed 5 % in most cases.



DIMENSIONAL TOLERANCES

Thickness (inches)	Thickness Tolerance (% of Thickness)	Width Tolerance (inches)	Length Tolerance (inches)	Flatness Deviation (% Maximum)
.1875 to .500	± 4	+ .125 -0	+ .125 -0	3
Over .500 to 1.000	± 5	+ .125 -0	+ .125 -0	5
Over 1.000 to 1.500	± 5	+ .1875 -0	+ .1875 -0	6

Plate will be sheared, abrasive cut, band saw cut, or water jet cut to the tolerances shown.

The deviation from flatness is determined by the formula:

$$H/L \times 100 = \% \text{ Flatness Deviation}$$

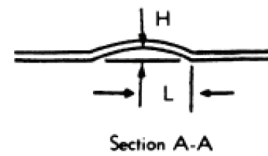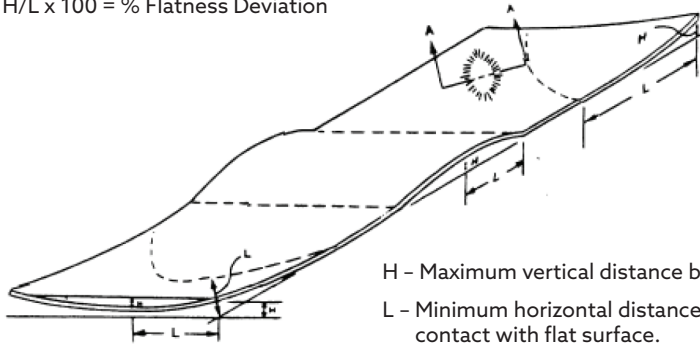

H - Maximum vertical distance between flat surface and lower surface of sheet.

L - Minimum horizontal distance between highest point on sheet and point contact with flat surface.

SURFACE CONDITION

The plate will be supplied with a matte finish. It will be of uniform quality, clean and free from foreign matter. Major surface defects will be removed by grinding provided that such conditioning does not reduce dimensions below specified limits.

Hazards identification in Advertising (Directive 67/548/EEC Article 26, Directive 1999/45/EC Article 13 and REGULATION (EC) No 1272/2008 Article 48) none.

IDENTIFICATION

The material will be identified with appropriate specification number, ingot or lot number, and nominal size. Shipping containers will be marked with the name of the customer and the purchase order number.

REJECTION

Elmet Technologies must receive written notification of rejected material with the reason for rejection. The right is reserved to inspect rejected material at customer plant for claim validation. The material may be returned only after proper authorization.



ELMET TECHNOLOGIES

1560 Lisbon Street • Lewiston, Maine 04240

P +1.207.333.6100

sales@elmettech.com

www.elmettechnologies.com

The conditions of your use and application of Elmet Technologies products, technical assistance, and information (whether verbal, written or by way of production evaluations), including any suggested formulations and recommendations, is your responsibility. Therefore, you are encouraged to test our products and review any technical assistance and/or information you may receive from Elmet Technologies with your own resources, and determine to your own satisfaction whether Elmet Technologies products are suitable for your intended uses and applications. This application-specific analysis should include at minimum testing to determine suitability for the intended use from a technical as well as health, safety, and environmental standpoint. Any technical assistance and/or information provided by Elmet Technologies is given without any express or implied warranty or guarantee. You agree and understand and hereby expressly release Elmet Technologies from all liability, in tort, contract or otherwise, incurred in connection with the use of our products, technical assistance and/or information, except as may be contained otherwise in a written agreement between you and Elmet Technologies. Any statement or recommendation not contained herein or in a written agreement between you and Elmet Technologies is unauthorized and shall not bind Elmet Technologies. Nothing herein shall be construed as a recommendation to use any Elmet Technologies products in a manner violative of the intellectual property rights of any third party. No license is implied or granted under or to Elmet Technologies intellectual property. All product deliveries are based on the then current product specification and Elmet Technologies' Conditions of Sale. IN NO EVENT WILL ELMET TECHNOLOGIES BE LIABLE FOR INCIDENTAL OR CONSEQUENTIAL DAMAGES.